

Effect of hydrogen on the magnetic properties of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2$ and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$

S. Annapoorni, G. Markandeyulu, and K. V. S. Rama Rao

Citation: *Journal of Applied Physics* **65**, 4955 (1989); doi: 10.1063/1.343213

View online: <http://dx.doi.org/10.1063/1.343213>

View Table of Contents: <http://scitation.aip.org/content/aip/journal/jap/65/12?ver=pdfcov>

Published by the [AIP Publishing](#)

Articles you may be interested in

[Effect of Ni substitution on the magnetic and electrical properties of \$\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\$](#)

J. Appl. Phys. **77**, 4589 (1995); 10.1063/1.359423

[Investigation of magnetic, magnetomechanical, and electrical properties of the \$\text{Tb}_{0.27}\text{Dy}_{0.73}\text{Fe}_{2-x}\text{Co}_x\$ system](#)

J. Appl. Phys. **73**, 1380 (1993); 10.1063/1.353258

[Ferromagnetic resonance studies on \$\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x\$ and \$\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x\$ systems](#)

J. Appl. Phys. **68**, 1394 (1990); 10.1063/1.346695

[5 \$^{57}\text{Fe}\$ Mossbauer studies on \$\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x\$ and \$\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x\$](#)

J. Appl. Phys. **67**, 424 (1990); 10.1063/1.345275

[Abstract: Low frequency magnetoelastic effects in \$\text{Tb}_{0.27}\text{Dy}_{0.73}\text{Fe}_2\$](#)

J. Appl. Phys. **49**, 1995 (1978); 10.1063/1.324775



Effect of hydrogen on the magnetic properties of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2$ and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$

S. Annapoorni, G. Markandeyulu, and K. V. S. Rama Rao^{a)}

Magnetism and Magnetic Materials Laboratory, Department of Physics, Indian Institute of Technology, Madras-600 036, India

(Received 24 October 1988; accepted for publication 25 January 1989)

X-ray powder photographs on $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ ($x = 0-3.1$) and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$ ($x = 0-3.3$) revealed that there is an expansion of the lattice upon hydrogenation.

Magnetization measurements were performed using a PAR vibrating sample magnetometer in the temperature range 100–700 K. The total magnetic moment is found to decrease with increase of hydrogen content. The Curie temperature of the hydrides is considerably lowered, though the exact T_C in hydrides could not be determined due to desorption. Both $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2$ and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$ do not exhibit any compensation, whereas T_{comp} is observed and found to decrease with x in the case of the $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ system, $x = 0.18-3.1$. No compensation was observed even in the hydrides of the $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$ system. The temperature variation of magnetization of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$ suggests the occurrence of a spin-reorientation transition.

I. INTRODUCTION

The rare-earth-transition-metal (RE-TM) intermetallic compounds are reported to absorb large quantities of hydrogen to form stable hydrides.¹ There is a large change in the unit cell volume and also in the 3d electron interaction upon hydrogenation.^{1,2} Studies on RECo_2 compounds showed that the cobalt moment gets reduced on hydrogen absorption.³ The iron moment in the case of REFe_2 compounds increases,⁴ whereas hydrogen induces magnetic moment on Mn in the case of rare-earth-manganese systems.⁵ The RENi_2 compounds after hydrogenation turn out to be amorphous.⁶

The REFe_2 ternary cubic Laves-phase compounds, particularly $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2$ and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$, are drawing considerable interest in recent years as possible magnetostrictive transducer elements.^{7,8} In these compounds, magnetic properties such as magnetization, Curie temperature, compensation temperature,⁹⁻¹¹ and spin reorientation¹² have been investigated. The effect of hydrogen on their magnetic properties is presented in this paper.

II. EXPERIMENTAL DETAILS

The alloys were prepared by arc melting the constituent elements of 99.9% purity in argon atmosphere at a pressure of 700 Torr and remelted several times to ensure homogeneity. The weight loss of the arc-melted samples was less than 1%. The samples were annealed in vacuum at 1173 K for 2 weeks. X-ray powder photographs showed the formation of a single phase with MgCu_2 -type structure.

The hydrogenated samples were prepared using the volumetric method working in the pressure range $1.0 < P_H / \text{Torr} < 760$ and a temperature range $300 < T / \text{K} < 1173$.¹³ The samples were activated by exposing them to hydrogen at a pressure of 700 Torr and a temperature of 473 K. In order to get different hydrogen concentrations, the samples were exposed to different temperatures and hydrogen pressures, and

the amount of hydrogen absorbed was determined from the change in volume. The hydrogenated samples were prepared by quenching (ice-water mixture) from suitable conditions of pressure and temperature, and then quickly exposing to atmosphere to avoid further absorption.

Magnetization measurements were performed using a PAR vibrating sample magnetometer in the temperature range 100–700 K. The temperature was maintained to an accuracy of ± 1 K. The measurements were carried out up to an applied field of 10 kOe.

III. RESULTS

A. $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$

Hydrogenated samples of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ with $x = 0.18, 0.4, 1.1, 2.0, 2.4,$ and 3.1 were prepared, and their Debye-Scherrer photographs showed the cubic Laves-phase structure. There is no crystallographic transformation for all the hydrides studied. From the powder photographs the lattice constants were determined. Figure 1 shows the variation of the lattice constant with hydrogen concentration.

The room-temperature (RT) magnetization curves for various concentrations of hydrogen are shown in Fig. 2. The magnetization of the hydrides is found to decrease with increasing hydrogen concentration. The hydrides with $x = 3.1$ exhibits paramagnetic behavior at RT.

The temperature variation of magnetization at an applied field of 10 kOe is shown in Fig. 3. From the figure it can be seen that the hydrides studied exhibit compensation temperature (T_{comp}). T_{comp} is found to decrease with the increase of hydrogen concentration.

The Curie temperature of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_{3.1}$ is found to be 280 K. The Curie temperature for other samples could not be determined due to the desorption of hydrogen (shown by dashed lines). Table I gives the lattice parameter, RT magnetization at 10 kOe, and T_{comp} for various concentrations of hydrogen.

^{a)} To whom all correspondence should be addressed.

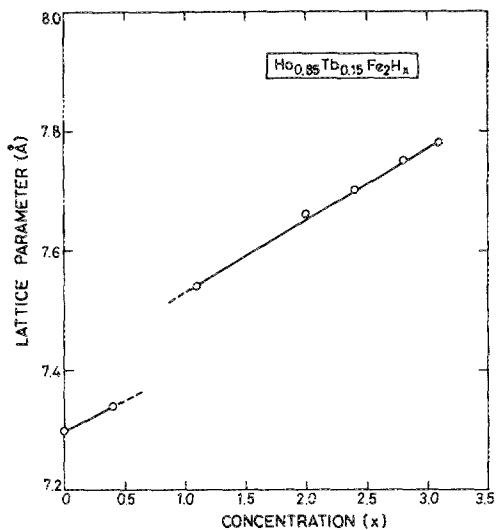


FIG. 1. Variation of lattice parameter of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ with x .

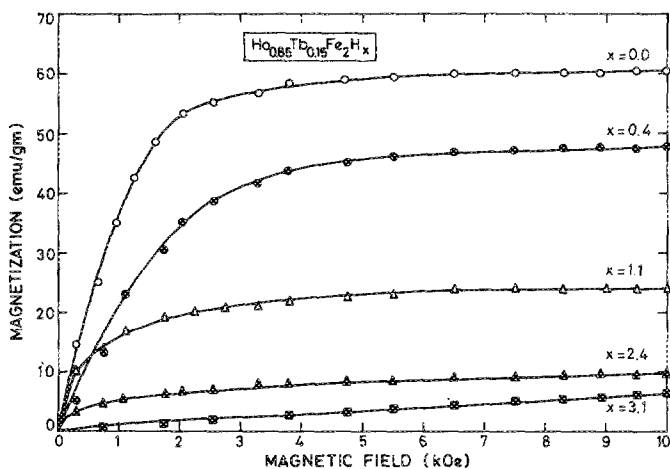


FIG. 2. RT magnetization curves of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$.

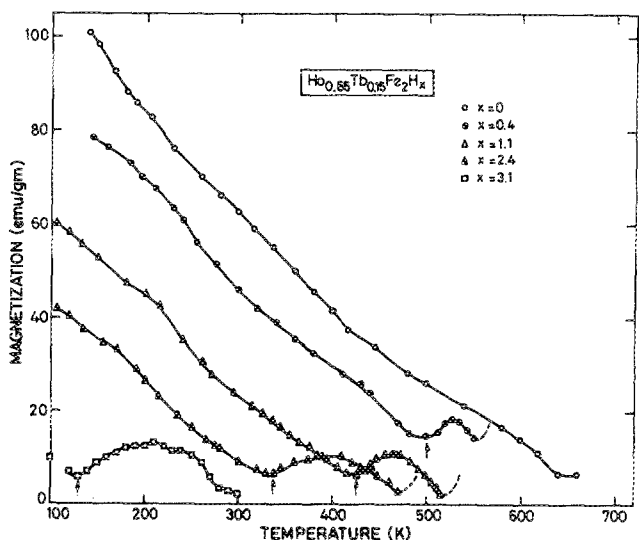


FIG. 3. Temperature variation of magnetization at an applied field of 10 kOe of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$. The arrows represent T_{comp} and the dashed lines desorption.

TABLE I. Lattice constants, RT magnetization at 10 kOe, and T_{comp} of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$.

x	Lattice Constant (Å)	RT magnetization at 10 kOe (emu/g)	T_{comp} (K)
0.0	7.30	62	...
0.4	7.34	47	500
1.1	7.53	24	420
2.0	7.67	13	385
2.4	7.70	8	330
3.1	7.78	3 ^a	130

^a Paramagnetic at 300 K.

B. $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$

Samples of concentration $x = 0.4, 0.9, 1.5, 1.9,$ and 3.3 were prepared. Powder Debye-Scherrer photographs showed cubic Laves-phase structure, and the lattice constant determined from the photographs is plotted as a function of x in Fig. 4. Figure 5 shows the RT magnetization of the hydrides for various concentrations. From the plot of temperature versus magnetization at 10 kOe in Fig. 6, it is seen that neither $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$ nor its hydrides exhibit compensation.

Table II shows the lattice constants and RT magnetization for various concentrations of hydrogen.

IV. DISCUSSION

The variation of lattice parameter with hydrogen for $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ ($x = 0-3.1$) and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$ ($x = 0-3.3$) showed a linear behavior (Figs. 1 and 4). The discontinuity shown by dotted line is due to the phase transition, the phase transition resulting in a large expansion of the lattice. This is a common feature observed in REFe_2 hydrides.^{14,15}

Hydrogen is reported to influence the magnetic moment

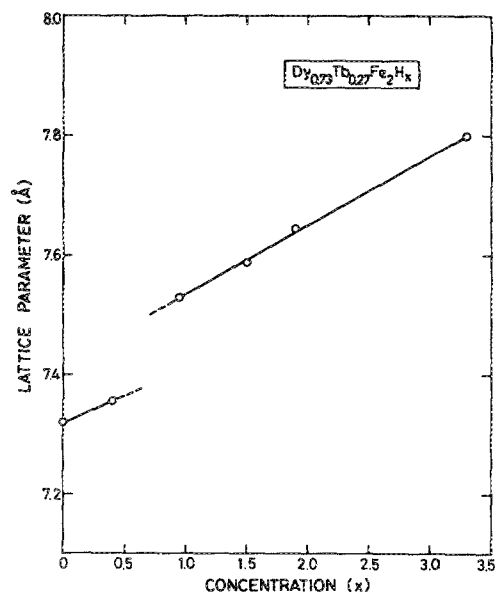


FIG. 4. Variation of lattice parameter of $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$.

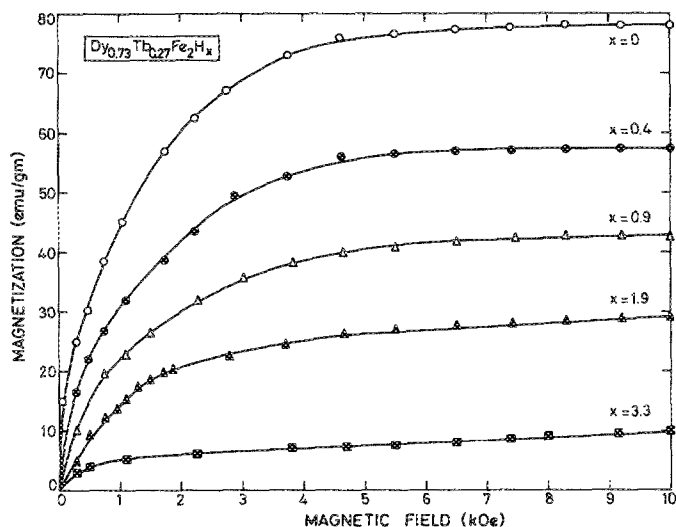


FIG. 5. RT magnetization curves of $Dy_{0.73}Tb_{0.27}Fe_2H_x$.

of the transition metal modifying the d -band structure, whereas there is an indirect effect on the rare earth due to the low-lying $4f$ levels.¹⁶ Recently, Berthier *et al.*¹⁷ from the zero-field nuclear magnetic resonance (ZNMR) of ^{159}Tb studies on $TbFe_2H_x$ showed that the magnetic moment on Tb remained constant with hydrogen concentration up to a value of $x = 3.5$, while the magnetization measurements showed a decrease in the total moment upon hydrogenation. In the $DyFe_2H_x$ system the Mössbauer studies¹⁸ showed that the Dy moment remains almost unchanged upon hydrogen absorption, while the Fe moment increases slightly as in the case of $TbFe_2H_x$. On the other hand, neutron-diffraction studies on $HoFe_2D_{3.5}$ by Fish *et al.*¹⁹ showed a decrease in the RE magnetic moment while the Fe moment slightly increases, thereby causing a large decrease in the total magnetic moment compared to $TbFe_2H_x$ and $DyFe_2H_x$. The RT magnetization of the hydrides of $Ho_{0.85}Tb_{0.15}Fe_2$ and $Dy_{0.73}Tb_{0.27}Fe_2$ decreases with increasing hydrogen content (x). The variation of RT magnetization of

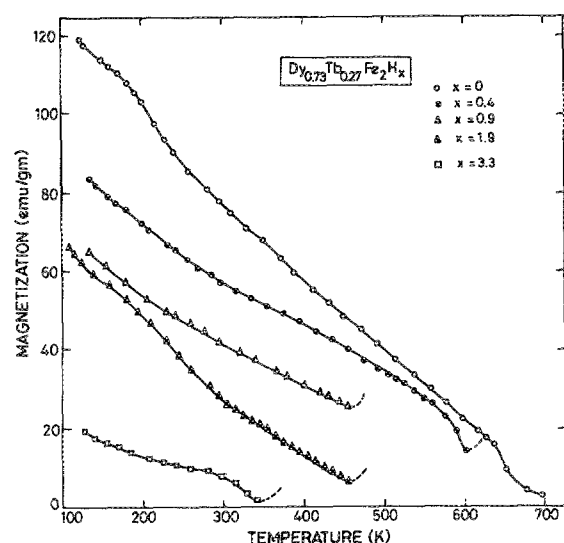


FIG. 6. Temperature variation of magnetization at an applied field of 10 kOe of $Dy_{0.73}Tb_{0.27}Fe_2H_x$. The dashed lines show desorption.

TABLE II. Lattice constants and RT magnetization at 10 kOe of $Dy_{0.73}Tb_{0.27}Fe_2H_x$.

x	Lattice constant (\AA)	RT magnetization at 10 kOe (emu/g)
0.0	7.32	78
0.3	7.33	69
0.4	7.35	57
0.9	7.53	45
1.9	7.65	30
3.3	7.80	8

$Ho_{0.85}Tb_{0.15}Fe_2H_x$ and $Dy_{0.73}Tb_{0.27}Fe_2H_x$ with x is shown in Fig. 7. It is seen from the figure that the change of magnetization with x in the case of $Ho_{0.85}Tb_{0.15}Fe_2H_x$ system is faster than in the case of $Dy_{0.73}Tb_{0.27}Fe_2H_x$. This may be due to the fact that in the case of $Ho_{0.85}Tb_{0.15}Fe_2H_x$ the hydrogen induces a reduction in the Ho moment and a slight increase in the Fe moment as in $HoFe_2H_x$, whereas in the case of $Dy_{0.73}Tb_{0.27}Fe_2H_x$ there is no effect on the RE moment upon hydrogenation and only the iron moment increases as in the case of $DyFe_2H_x$ and $TbFe_2H_x$ systems. This can be confirmed by ^{57}Fe Mössbauer studies and ZNMR studies on the RE ions.

The hydrides of $Ho_{0.85}Tb_{0.15}Fe_2$ are found to exhibit compensation, with the compensation temperature (T_{comp}) decreasing with the increase of hydrogen content. This may be due to a rapid decrease in the molecular field on the Ho ion and also a reduction in the RE-RE exchange upon hydrogenation. No compensation is observed in $Ho_{0.85}Tb_{0.15}Fe_2$ and $Dy_{0.73}Tb_{0.27}Fe_2H_x$. This may be due to the large molecular fields present on the rare-earth ions in these systems.¹⁷

De Saxce, Berthier, and Fruchart¹⁴ have observed a deviation from the smooth behavior in the temperature variation of magnetization of $ErFe_2H_x$ and have attributed this to the spin-reorientation phenomena. In the present case, the

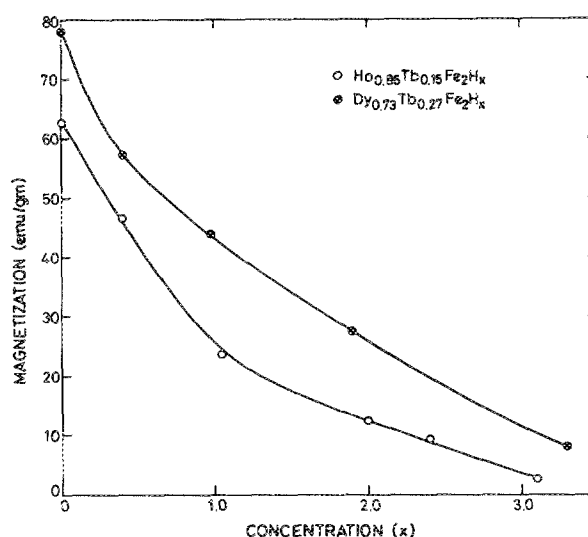


FIG. 7. Variation of RT magnetization at 10 kOe of $Ho_{0.85}Tb_{0.15}Fe_2H_x$ and $Dy_{0.73}Tb_{0.27}Fe_2H_x$ with x .

temperature variations of magnetization of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ (Fig. 3) and $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$ (Fig. 6) are found to exhibit deviations from a smooth behavior in the temperature region 220–280 K in the case of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2\text{H}_x$ and over a much wider range (not very well defined) in the case of $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2\text{H}_x$, and these are probably due to spin-reorientation phenomenon occurring in these systems. Seh and Nowik,²⁰ from the Mössbauer measurements on $\text{Ho}_{0.9}\text{Tb}_{0.1}\text{Fe}_2$, inferred that the easy direction of magnetization changes from [110] to [100] over a temperature range 220–260 K, whereas in the case of $\text{Dy}_{0.7}\text{Tb}_{0.3}\text{Fe}_2$ the easy direction of magnetization changes from [111] to [100] over a temperature range 180–260 K.

The Curie temperature (T_C) of $\text{Ho}_{0.85}\text{Tb}_{0.15}\text{Fe}_2$ is around 630 K and is about 660 K in the case of $\text{Dy}_{0.73}\text{Tb}_{0.27}\text{Fe}_2$. In the case of the hydrides the Curie temperature tends to decrease (see Figs. 3 and 6) with increasing hydrogen content, as seen by the tendency of the graph to follow the dotted lines (however, this could not be observed experimentally, as the desorption occurred at temperature lower than the supposed T_C). This reduction has been attributed to the decrease in the Fe-Fe exchange which is predominant in these systems.¹⁹

ACKNOWLEDGMENT

The authors wish to thank the Department of Electronics, Government of India for supporting this research program.

- ¹H. H. Van Mal, K. H. J. Buschow, and A. R. Miedema, *J. Less-Common Met.* **49**, 473 (1976).
- ²H. H. Van Mal, K. H. J. Buschow, and A. R. Miedema, *J. Less-Common Met.* **35**, 65 (1974).
- ³F. A. Kuipers, *Philips Res. Rep. Suppl.* **1973**, 72 (1973).
- ⁴K. H. J. Buschow, *Physica* **86–88B**, 79 (1977).
- ⁵K. H. J. Buschow and R. C. Sherwood, *J. Appl. Phys.* **48** (1977).
- ⁶K. Aoki, T. Yamamoto, and T. Masumoto, *Scr. Metall.* **21**, 27 (1987).
- ⁷A. E. Clark and H. T. Savage, *IEEE Trans. Sonics Ultrason.* **SU-22**, 50 (1975).
- ⁸N. C. Koon, A. I. Schindler, C. M. Williams, and F. C. Carter, *J. Appl. Phys.* **45**, 5389 (1974).
- ⁹A. E. Clark, R. Abbundi, and W. R. Gillmor, *IEEE Trans. Magn.* **MAG-14**, 542 (1978).
- ¹⁰G. F. Clark, B. K. Tanner, and H. T. Savage, *Philos. Mag. B* **46**, 331 (1982).
- ¹¹P. Westwood, J. S. Abeli, and K. C. Pitmann, *IEEE Trans. Magn.* **MAG-24**, 1873 (1988).
- ¹²U. Atzmony, M. P. Dariel, E. R. Bauminger, D. Lebenbaum, I. Nowik, and S. Ofer, *Phys. Rev. B* **7**, 4220 (1973).
- ¹³N. Rajalakshmi, Ph. D. thesis, Indian Institute of Technology, Madras, 1987.
- ¹⁴T. De Saxce, V. Berthier, and D. Fruchart, *J. Less-Common Met.* **107**, 35 (1985).
- ¹⁵D. Fruchart, V. Berthier, T. De Saxce, and P. Vuillet, *J. Less-Common Met.* **130**, 89 (1987).
- ¹⁶W. E. Wallace, S. K. Malik, T. Takeshita, S. G. Sankar, and D. M. Gualtieri, *J. Appl. Phys.* **49**, 1486 (1978).
- ¹⁷V. Berthier, T. De Saxce, D. Fruchart, and P. Vuillet, *Physica B* **130**, 520 (1985).
- ¹⁸P. J. Viccaro, J. M. Friedt, D. Niarchos, B. D. Dunlap, G. K. Shenoy, A. T. Aldred, and D. G. Westlake, *J. Appl. Phys.* **50**, 2051 (1979).
- ¹⁹G. E. Fish, J. J. Rhyne, S. G. Sankar, and W. E. Wallace, *J. Appl. Phys.* **50**, 2003 (1979).
- ²⁰M. Seh and I. Nowik, *J. Magn. Magn. Mater.* **22**, 239 (1981).